

ΣΥΝΕΔΡΙΑ ΤΗΣ 16<sup>ΗΣ</sup> ΜΑΡΤΙΟΥ 2000

ΠΡΟΕΔΡΙΑ ΝΙΚΟΛΑΟΥ ΑΡΤΕΜΙΑΔΟΥ

---

**ΜΗΧΑΝΙΚΗ. – A breakthrough in visualizing the Theocaris interphase with thermal atomic force microscopy\***, by Matthew S. Tillman, James C. Seferis\*\*, corresponding member of the Academy of Athens and Pericles S. Theocaris, Academy of Athens.

**ABSTRACT**

Previous work in the characterization of interphase regions in thermosetting composite systems has focused on the inference of an interphase layer from effects noticed through macroscale mechanical and thermal testing. With the development of atomic force microscopy and active thermal probes for this technique, it is now possible to examine material thermal properties on a much smaller scale. Variations in microscale thermal properties of a aerospace grade thermosetting resin system were evaluated for carbon and glass fiber reinforcement using the modulated local thermal analysis mode of a Thermal atomic force microscope. The variations observed clearly demonstrate the presence of a soft interphase layer in the glass material, and underline the importance of fiber/matrix interactions during the formation of the interphase.

**Introduction**

For many years, the study of fiber reinforced composite materials has focused on the structure-property relations that could be developed to describe the heterogeneity that existed in these materials. With the development of the

---

\* Συμβολή στο έρευνητικό έργο του 'Ακαδημαϊκού Περικλή Θεοχάρη.

\*\* MATTHEW S. TILLMAN, ΔΗΜΗΤΡΙΟΥ Κ. ΣΕΦΕΡΗ, Συμβολή στην ανάδειξη τής κατά Θεοχάρη μεσοφάσεως μέσω τής μικροσκοπίας θερμικών δυνάμεων άτομικής κλίμακας.

process-structure-property methodology by Seferis and Theocaris in the 1980's [1], the focus of material evaluation changed to include the effects of processing parameters on the final characteristics of polymeric composites. To this end, the evaluation and characterization of microscale material structure-property changes with variation in processing conditions has led to an increased understanding of the effect of the interphase region on the performance of composite materials.

The reasons for the formation of this interphase region have been examined in depth by many researchers. Several inclusive reviews of this material are presented by Hughes, as well as Shorthall and Yip [2-4], while a comprehensive presentation is given by Theocaris [5]. It is in this volume that Theocaris presents his models for the development of interphases in composite materials, one of which is presented in Figure 1. In this model, which represents the interphase as a cylinder around the fiber, the resin properties vary in the radial direction in the interphase layer. However, the boundary conditions of the layers are such that the fiber and matrix properties do not vary with radial position.

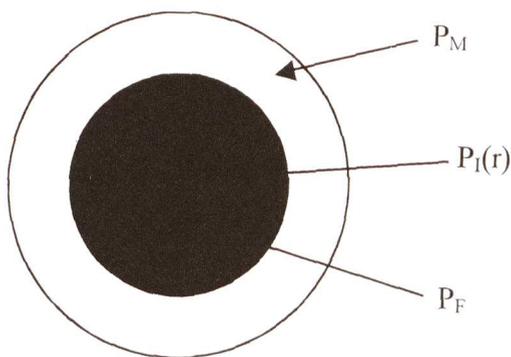


Figure 1: Transverse schematic of the three layer interphase model proposed by Theocaris.

Interestingly enough, a considerable body of work has been amassed regarding the inference of fiber interphase properties from the measurement of mechanical tests [6-11]. In some cases, these mechanical tests have been related to thermodynamic/kinetic models that provide a theoretical description of resin property variance near the fiber surface [12, 13]. While no clear evaluation of the structure of the matrix interphase had been performed, there was evidence

to support variation of resin structure near fibers. This came primarily through the use of infrared spectroscopy of substrates coated in epoxy based resins [14-16]. While this type of isolated evaluation does not provide the structure for interphase regions within laminated structures, it clearly shows that carbon fibers have a measurable effect on the curing kinetics of epoxy based resin systems.

With the development of the atomic force microscope (AFM) [17], new tools were added to the evaluation of interphase phenomena. This methodology, based on the use of mechanical force to probe the structure and properties of a specimen, has found widespread application in nanoscale materials science. In analysis of composite materials, the use of normal stiffness measurements to evaluate the resin modulus near the carbon fiber have been very successful, showing a clear link between the formation of the interphase layer and the mechanical and structural properties of the resin [18, 19]. The growth of additional applications for atomic force microscopy has resulted in a large body of research focusing on the acquisition of microstructural knowledge of various materials.

The development of Scanning Thermal Microscopy (SThM) has allowed researchers to evaluate the microscale thermal properties of materials. The use of a passive thermal probe to evaluate heat generation in small-scale devices has been very successful [20-24]. This technique uses a nanofabricated thermocouple to evaluate variations in temperature with a resolution of less than 100 nm [21, 23]. While this technique has found numerous applications in electronics research, it is limited due to the passive nature of the scanning probe. As such, it is not able to detect property-based variations on the microscale.

The development of an active thermocouple probe for use in SThM by Dinwiddie and coworkers has revolutionized the field of microscale materials analysis [25-27]. Using an SThM probe manufactured of wire made by the Wollaston process (5 micron diameter platinum core surrounded by a 75 micron diameter silver sheath), the developers produced a device that acted as a miniature thermocouple and a resistive heating element simultaneously. When this probe is coupled with an atomic force microscope, it is possible to resolve material differences based on thermal properties instead of mechanical force.

As in the case of traditional AFM, the probe is held in contact with the specimen using a feedback control loop to maintain a constant load on the surface. Using a separate feedback loop to maintain the probe at a fixed temperature [28], it is possible to raster the cantilever over the surface of the specimen and

generate a thermal map of the material. This provides information about the localized thermal conductivity of the specimen, and allows for visualization of the microscale heterogeneity in composite materials. This method is referred to as two-dimensional thermal scanning (2DThS).

In addition, 2DThS can be used to examine the subsurface morphology of a system. Through a modulation of the probe temperature in the 2DThS mode of operation, Reading and others found that the thermal probing depth could be varied by changing the frequency of modulation [28, 29]. This type of analysis has been used to examine metallic structures beneath the surface of polymeric materials, and to observe dynamic behavior in polymeric blends.

Once the microscale morphology of a specimen has been evaluated, localized variations in thermal properties can be evaluated using Local Thermal Analysis (LTA). Local thermal analysis involves modifying the probe temperature according to a programmed thermal ramp. By comparing the response of the active probe to a reference probe, differential thermal analysis (DTA) can be performed on a sample with a size of several cubic microns [30]. Much like macroscopic thermal analysis techniques, a sinusoidal variation in the temperature can be superimposed on the nominal temperature profile, resulting in a modulated LTA (m-LTA). This addition of a sinusoidal modulation to the linear temperature ramp allows a lock-in amplifier to increase the signal to noise ratio, making data analysis easier. A distinct difference exists between macroscale thermal analysis techniques and the use of LTA, since the thermal probe acts as both a heating element and a temperature sensor, while the two are separate on a DTA or a DSC. As is the case with macroscale modulated thermal analysis, the phase angle and modulation amplitude play a role in evaluating materials.

Craig and others have used m-LTA to examine microscale transitions in various thermoplastic materials and pharmaceuticals [31-35]. Using the onset of troughs and peaks in the first derivative of the modulated temperature phase, they identified the glass transition, recrystallization, and melting of the materials. The results of these experiments correlated well to similar experiments performed using DSC. In addition, the use of 2DThS in these two-phase systems allowed the researchers to evaluate the phase morphology of the materials.

The development of active probe SThM technology provides an exciting new method for the analysis of composite materials [36, 37]. Through the composite methodology developed by Seferis [1, 38, 39], an understanding of the processing-structure-property relationships in a polymeric composite relates material properties in the laboratory to the performance of those materials on

the manufacturing scale. Since micro-thermal analysis allows microstructure exploration of the processing-structure-property relationship, it has become a useful tool in understanding polymeric composites.

In this respect, the thermal atomic force microscope is a unique instrument. The experimental techniques described above provide a method of simultaneously accessing both the processing-structure and processing-property relations through the use of two-dimensional thermal scanning and local thermal analysis, respectively. The additional ability to analyze microscale changes in material properties such as the glass transition temperature ( $T_g$ ) and thermal expansion unlock a new level of information for the study of interphase behavior.

The purpose of this work was to evaluate the interphase properties of a commercial aerospace composite system using active thermal atomic force microscopy. This was realized through the exploration of process-structure-property relations on the microscale, and the relation of observed effects to thermal analysis performed on the macroscale. Finally, the resulting interphase analysis was interpreted with respect to the life-cycle performance of composite materials in the aircraft environment.

## Experimental

To evaluate the microscale presence of interphase regions in aerospace composites, materials were chosen to enable the effects of resin variation to be eliminated. To accomplish this, a commercial aerospace grade material was used that is available with a single resin impregnated into a wide variety of fiber types. Two twenty ply laminates were constructed of this material with the fiber reinforcement as either an 8 Harness Satin 7781 style fiberglass or a plain weave Toray T300 carbon fiber. To prevent the formation of voids due to air entrapment, the laminates were debulked between plies during lay-up. These laminates were cured simultaneously in a Lipton autoclave as per the manufacturers curing recommendations, which call for a pressure of 310 kPa (45 psig) and a 2.78°C/min (5°F/min) ramp to 177°C (350°F), a two hour hold at 177°C, and a 2.78°C/min cool down to room temperature.

To ensure resin consistency between the two materials used, laminates were examined for their macroscopic thermal behavior using a TA Instruments 2980 DMA. To evaluate the glass transition temperature of the materials, the instrument was used in a single frequency oscillatory mode with a temperature ramp

of 5 °C/min from room temperature to 250 °C, a frequency of 1 Hz, and an oscillation of 10 μm. The glass transition temperature was evaluated from the onset of the drop in the storage modulus.

To evaluate changes in the glass transition temperature near the fibers in these materials, cross-sections of each laminate were polished. Final surface polishing was done using 0.3 micron Al<sub>2</sub>O<sub>3</sub> grit. The polished specimens were then examined using a TA Instruments 2990 Micro-Thermal Analyzer (μTA) with a TopoMetrix thermal probe (TopoMetrix model number 1615-00). Probe temperature calibration was performed using room temperature (23 °C) and the melting points of PETG (T<sub>m</sub> = 165 °C), Nylon 6 (T<sub>m</sub> = 210 °C), Nylon 6,6 (T<sub>m</sub> = 247 °C) and Nylon 4,6 (T<sub>m</sub> = 277 °C). A linear interpolation of probe resistance as a function of temperature was used to provide a calibration curve over the temperature range of interest. Using the modulated local thermal analysis mode of the Micro-Thermal Analyzer, the probe temperature was ramped from 50 °C to 350 °C at a rate of 25 °C/sec. For all experiments detailed in this paper, the LTA temperature was modulated with an amplitude of 2 °C at a frequency of 2.2 kHz, and data was collected at a rate of 150 data points per second.

Suitable locations for interphase analysis were selected on the basis of several thermal and topographical scans, conducted at a temperature of 100 °C, a scanning frequency (scan velocity/scan length) of 2 Hz and a resolution of 200 lines per scan. These focused on the edge of fiber tows that was near a pocket of resin in the cured laminate. From these scans, fibers were selected if they were near a resin rich region that could be evaluated easily using local thermal analysis. It was important to select fibers near these resin rich regions so that a bulk T<sub>g</sub> could be obtained to normalize the glass transition temperatures near the fiber.

A series of these experiments was performed on each laminate. Glass transition temperatures were obtained by evaluating the onset point of the drop in the micro-TMA signal, corresponding to a softening of the matrix material. These temperatures were then normalized based on each specimen's bulk T<sub>g</sub> (T<sub>g,bulk</sub>) as determined through μTA measurements far away from the fibers. This accounts for probe and specimen based heat transfer effects that shift the measured T<sub>g</sub> to higher temperatures than the actual T<sub>g</sub> [37]. To normalize the T<sub>g</sub> values, equation 1 was used.

$$T_{g,\text{normalized}} = \frac{T_g}{T_{g,\text{bulk}}} \quad (1)$$

Following this, the distance from the center of the fiber was normalized using equation 2. Distances were measured using the position coordinates of the selected LTA locations ( $X_{LTA}$  and  $Y_{LTA}$ ), the coordinates of the fiber center ( $X_{fc}$  and  $Y_{fc}$ ), and the radius of the fiber in question ( $R$ ), which was determined using topographic feature measurement functions integrated in the  $\mu$ TA controller software.

$$\frac{r}{R} = \frac{\sqrt{(X_{LTA} - X_{fc})^2 + (Y_{LTA} - Y_{fc})^2}}{R} \quad (2)$$

## Results

To ensure that the matrix material from the two systems had the same constituents, the results from the DMA analysis were evaluated as compared to the manufacturer's product specification. As shown in Figure 2, the DMA results indicate that the materials have identical  $T_g$  values when evaluated using a macroscopic thermal analysis technique, and that this value corresponds to the glass transition temperature provided by the manufacturer. However, the glass

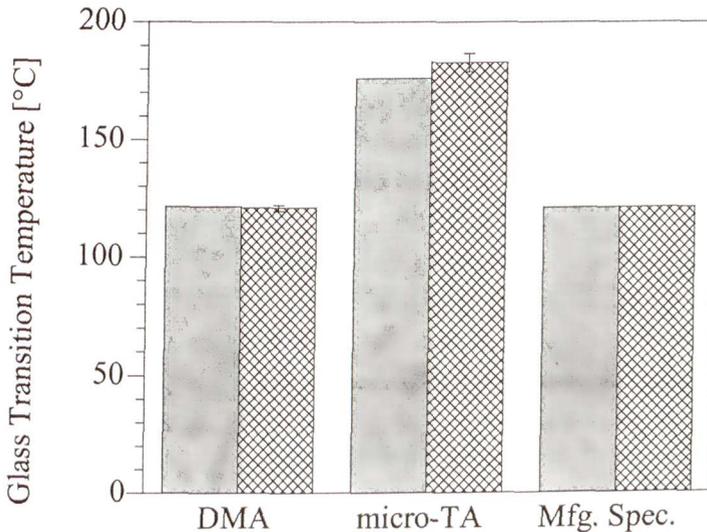


Figure 2: Measured glass transition temperatures for commercial aerospace resin system on glass (solid gray) and carbon (crosshatched).

transition temperatures obtained using the  $\mu$ TA are shifted to a higher temperature than those obtained using the DMA. This is the result of contact area dominated heat transfer effects on the microscale that artificially increase the temperatures measured using the  $\mu$ TA [37, 40, 41]. As discussed previously, this is the reason for normalization of the measured glass transition temperatures obtained using the micro-thermal analyzer.

Using the 2DThS mode of the  $\mu$ TA, it was possible to visualize the structure of the cured carbon and glass laminates near the edges of fiber tows. As shown in Figure 3, the carbon and glass materials have different sizes and packing densities in the cured composite. Also, it is worth noting that while the region of carbon reinforced material shown below would make an excellent candidate for LTA (due to the large resin region to the right of the fiber bed), the presence of transverse oriented fibers prevents LTA from being performed on the glass materials.

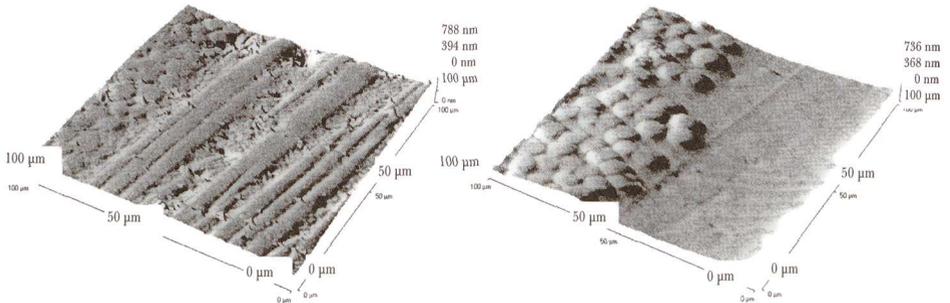


Figure 3: Topographical analyses of experimental laminates with glass (left) and carbon (right) reinforcement.

The evaluation of the glass transition variation with radial position from a fiber in the glass fiber reinforced material is presented in Figure 4. As shown, the glass transition temperature of the material drops near the fiber surface to approximately 85% of the bulk value. This result supports the soft interphase theory presented by several authors [6, 12, 13]. While most research in the past has focused on the development of interphases for carbon fibers, Tsai and coworkers have found evidence for a soft interphase in glass fiber materials [6].

In the case of the carbon fiber material, presented in Figure 4, the interphase is not as evident. While there is a small drop in glass transition temperature near the fiber, this is most likely due to scatter introduced through data

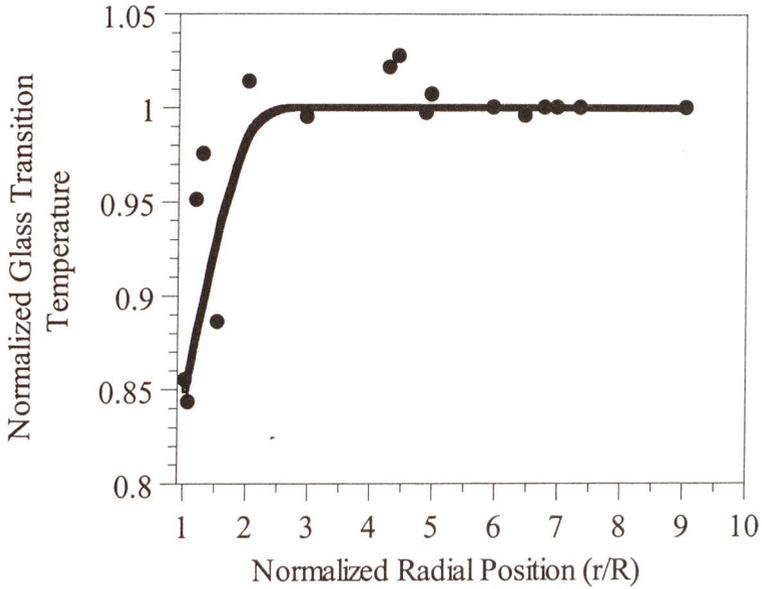


Figure 4: Observed decrease in  $T_g$  near glass fibers for commercial aerospace resin system.

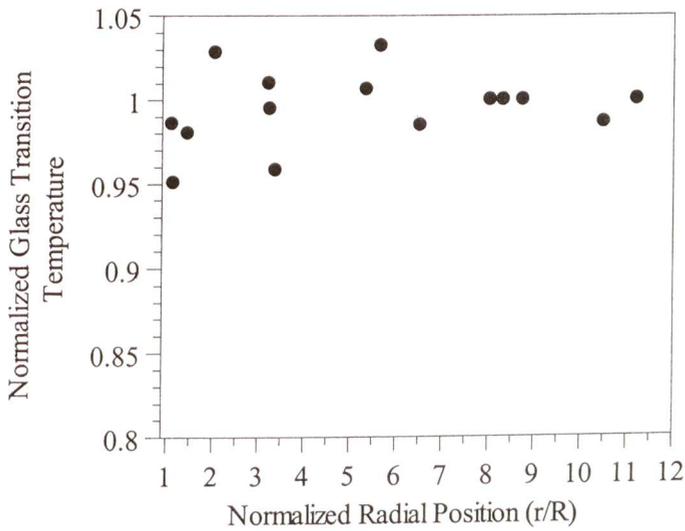


Figure 5: Observed decrease in  $T_g$  near carbon fibers for commercial aerospace resin system.

normalization. Since no clear interphase behavior was observed, the logical conclusion must be drawn that the interphase dimension is smaller than the minimum probe resolution for this technique.

## Discussion

In evaluating the importance of this finding, it is understand these results in relation to the end uses of these materials. As such, development of an understanding for the role of composites in the aircraft environment has been crucial. With the lower  $T_g$  of the resin matrix near the glass fibers, we have evidence that this aerospace resin system displays a long-range, soft interphase when it is impregnated and cured in glass fibers. In terms of durability, a soft interphase would result in lowered mechanical properties near the fibers in a laminate [42]. Since the matrix material nearest the fibers is expected to transfer the load from fibers to bulk matrix when the material is stressed, a lower strength and stiffness in this region will lead to reduced load transferring efficiency and possibly failure near the fibers. Of course, any failure near a fiber will tend to propagate down the length of the fiber at high speed, causing large scale fibrous delamination and part failure.

In addition, since the interphase region around the glass fibers is of lower crosslink density than the bulk matrix, it is more susceptible to moisture ingestion. Unfortunately, this will also lead to a lowering of the mechanical properties, and hasten the failure of a part. As such, intimate knowledge of the interphase region's properties, and the subsequent ability to control those properties is of paramount importance in designed composite structures.

Alternatively, in the case of the carbon material, one expects the loads on the composite to be transferred more uniformly, and with greater efficiency. Since the interphase is relatively small, and regions close to the fiber exhibit the same  $T_g$  as the bulk, the interphase region must have less of an effect on the mechanical performance of this material than it does in the case of the glass reinforced material.

On a broader scale, since the soft interphase region is large, and less efficient at transferring loads, the overall mechanical performance of the part will be decreased. As such, it is important to understand the phenomena that lead to the formation of interphase regions in composite materials, and thereby tailor the

interphase for maximum performance. Now that the technology of active thermal atomic force microscopy has been utilized to evaluate the presence of the interphase, characterization of various material interphases is no longer a matter of inferring their presence from mechanical tests.

## Conclusions

In this paper, the interphase thermal properties of a commercial aerospace composite resin system were evaluated. It was found that fiber type plays a significant role in the generation of the interphase. Micro-thermal analysis was employed to provide an effective method of measuring variations in glass transition temperature in near fibers in the cured laminates, and this data confirmed the presence of a soft interphase near glass fibers, but did not reveal the presence of an interphase near the carbon fibers. Collectively, this work provides a new methodology for directly evaluating the interphase thermal properties of composite systems, and clearly demonstrates the degree to which these systems can affect the performance of composite materials.

## Acknowledgements

The authors wish to acknowledge the contributions of the Boeing Company in funding this research. In addition, this research was supported by the sponsors of the global BEDR network at the Polymeric Composites Laboratory. Professor Theocaris has been an active part of this network since 1979, and his contributions have been vital to the growth and development of composite science and engineering at the University of Washington.

## REFERENCES

1. Seferis, J.C. and Theocaris, P.S., eds. *Interrelations Between Processing, Structure and Properties of Polymeric Materials*. Materials Science Monographs. Vol. 21. 1984, Elsevier: New York.

2. Shorthall, J.B. and Yip, H.W.C., The interfacial bond strength in glass fibre/polyester resin composite systems. Part 2: The effect of surface treatment, *Journal of Adhesion* **1976**, *8*, 155.
3. Shorthall, J.B. and Yip, H.W.C., The interfacial bond strength in glass fibre/polyester resin composite systems. Part 1: The measurement of bond strength, *Journal of Adhesion* **1976**, *7*, 311.
4. Hughes, J.D.H., The Carbon Fibre/Epoxy Interface - A Review, *Composites Science and Technology* **1990**, *41*, 13.
5. Theocaris, P.S., *The Mesophase Concept in Composites*. 1987, Berlin: Springer-Verlag. p. 292.
6. Tsai, H.C., Arocho, A.M., and Gause, L.W., Prediction of Fiber-Matrix Interphase Properties and their Influence on Interface Stress, Displacement and Fracture Toughness of Composite Material, *Materials Science and Engineering, A* **1990**, *126*, 295.
7. Williams, J.G., Donnellan, M.E., James, M.R., and Morris, W.L., Properties of the Interphase in Organic Matrix Composites, *Materials Science and Engineering, A* **1990**, *126*, 305.
8. Williams, J.G., James, M.R., and Morris, W.L., Formation of the interphase in organic matrix composites, *Composites* **1994**, *25*, 757.
9. Madhukar, M.S. and Drzal, L.T., Fiber-Matrix Adhesion and Its Effect on Composite Mechanical Properties: II. Longitudinal (0°) and Transverse (90°) Tensile and Flexure Behavior of Graphite/Epoxy Composites, *Journal of Composite Materials* **1991**, *25*, 958.
10. Drzal, L.T., Rich, M.J., and Lloyd, P.F., Adhesion of Graphite Fibers to Epoxy Matrices: I. The Role of Fiber Surface Treatment, *Journal of Adhesion* **1982**, *16*, 1.
11. Drzal, L.T., The Effect of Polymeric Matrix Mechanical Properties on the Fiber-Matrix Interfacial Shear Strength, *Materials Science and Engineering, A* **1990**, *126*, 289.
12. Skourlis, T.P. and McCullough, R.L., The Effect of Temperature on the Behavior of the Interphase in Polymeric Composites, *Composites Science and Technology* **1993**, *49*, 363.
13. Palmese, G.R. and McCullough, R.L., Kinetic and Thermodynamic Considerations Regarding Interphase Formation in Thermosetting Composite Systems, *Journal of Adhesion* **1994**, *44*, 29.
14. Sellitti, C., Koenig, J.L., and Ishida, H., Surface Characterization of Car-

- bon Fibers and Interphase Phenomena in Epoxy-reinforced Composites, *Materials Science and Engineering, A* **1990**, 126, 235.
15. Garton, A. and Daly, J.H., Characterization of the Aramid: Epoxy and Carbon: Epoxy Interphases, *Polymer Composites* **1985**, 6, 195.
  16. Wang, S. and Garton, A., The Effect of Carbon Surface Functionality on Tetrafunctional Epoxy Resin - Diaminodiphenylsulfone Cure Reactions, *Journal of Applied Polymer Science* **1990**, 40, 90.
  17. Binnig, G., Quate, C.F., and Gerber, C., Atomic Force Microscope, *Physical Review Letters* **1986**, 56, 930.
  18. Dagastine, R.R., *Interrogating the Interphase Region in Fiber Reinforced Composites Using Atomic Force Microscopy*, Bachelors in Chemical Engineering. 1997, University of Delaware: Newark, Delaware. p. 140.
  19. VanLandingham, M.R., *Characterization of Interphase Regions in Fiber-Reinforced Polymer Composite Materials*, Doctorate in Materials Science. 1997, University of Delaware: Newark, Delaware. p. 224.
  20. Zhou, L., Xu, G.Q., Li, S.F.Y., Ho, P.K.H., Zhang, P.C., Ye, K.D., Wang, W.J. and Lu, Y.F., Scanning thermal microscopy and atomic force microscopy studies of laser-induced deposited metal lines, *Applied Surface Science* **1997**, 120, 149.
  21. Balk, L.J., Cramer, R.M. and Fiege, G.B.M., Thermal Analyses by Means of Scanning Probe Microscopy, *Proceedings of the 6th International Symposium on the Physical & Failure Analysis of Integrated Circuits* **1997**, 1.
  22. Oesterschulze, E. and Kassing, R., Thermal and Electrical Imaging of Surface Properties with High Lateral Resolution, *Proc. of the 16th International conference on Thermoelectrics* **1997**, 719.
  23. Majumar, A., Thermal Microscopy and Heat Generation in Electronic Devices, *Microelectron. Reliab.* **1998**, 38, 559.
  24. Majumar, A. and Varesi, J., Nanoscale Temperature Distributions Measured by Scanning Joule Expansion Microscopy, *Journal of Heat Transfer* **1998**, 120, 297.
  25. Dinwiddie, R.B., Pylkki, R.J. and West, P.E., Thermal Conductivity Contrast Imaging with a Scanning Thermal Microscope, *Thermal Conductivity* **1994**, 22, 668.
  26. Maywald, M., Pylkki, R.J. and Balk, L.J., Imaging of Local Thermal and Electrical Conductivity with Scanning Force Microscopy, *Scanning Microscopy* **1994**, 8, 181.

27. Pylkki, R.J., Moyer, P.J. and West, P.E., Scanning Near-Field Optical Microscopy and Scanning Thermal Microscopy, *Japanese Journal of Applied Physics Pt. 1* **1994**, *33*, 3785.
28. Hammiche, A., Pollock, H.M., Song, M. and Hourston, D.J., Sub-Surface Imaging by Scanning Thermal Microscopy, *Measurement Science and Technology* **1996**, *7*, 142.
29. Hammiche, A., Song, M., Pollock, H.M., Reading, M. and Hourston, D.J., Sub-surface SThM Imaging of Blends, with Localised Calorimetric Analysis, *Polymer Preprints, ACS Division of Polymer Chemistry* **1996**, preprint number 278.
30. Hammiche, A., Reading, M., Pollock, H.M., Song, M. and Hourston, D.J., Localised Thermal Analysis Using a Miniaturised Resistive Probe, *Rev. Sci. Instrum.* **1996**, *67*, 4268.
31. Reading, M., Pollock, H., Hammiche, A. and Price, D.M., Advances in Material Characterization Through Imaging and Analysis on a Sub-Micron Scale, *Proc. 26th NATAS* **1998**, 122.
32. Reading, M., Hourston, D.J., Song, M., Pollock, H.M. and Hammiche, A., Thermal Analysis for the 21st Century, *American Laboratory* **1998**, *30*, 13.
33. Pollock, H.M., Hammiche, A., Song, M., Hourston, D.J. and Reading, M., Interfaces in polymer blends: SThM imaging, M-T DSC fingerprinting, *Polymer Preprints, ACS Division of Polymer Chemistry* **1996**, 69.
34. Hammiche, A., Hourston, D.J., Pollock, H.M., Reading, M. and Song, M., Scanning thermal microscopy: Subsurface imaging, thermal mapping of polymer blends, and localized calorimetry, *Journal of Vacuum Science and Technology B* **1996**, *14*, 1486.
35. Craig, D.Q.M., Royall, P.G., Reading, M., Price, D.M., Lever, T.J. and Furry, J., Micro-Thermal Analysis for the Characterisation of Pharmaceutical Materials, *Proc. 26th NATAS* **1998**, 610.
36. Tillman, M.S. and Seferis, J.C., Investigation of Manufacturing Effects on the Cured Thermal Properties of a Wet Lay-Up Thermoset Resin, *Proc. of the 45th SAMPE Symposium* **2000**, in press.
37. Tillman, M.S., Takatoya, T., Hayes, B.S. and Seferis, J.C., Evaluation of the Reproducibility of Micro-Thermal Analysis Measurements of Polymeric Specimens, *Proc. 4th Mediterranean Conference on Calorimetry and Thermal Analysis* **1999**, 122.

38. Seferis, J.C., Scaling Concepts for Composite Material Developments, *SAMPE Journal* **1998**, 24, 6.
39. Miller, A.G., Lovell, D.T. and Seferis, J.C., The Evolution of an Aerospace Material: Influence of Design, Manufacturing and In Service Performance, *Composite Structures* **1993**, 27, 193.
40. Dransfield, K. and Xu, J., The heat transfer between a heated tip and a substrate: fast thermal microscopy, *Journal of Microscopy Pr. 1* **1988**, 152, 35.
41. Nakabeppu, O., Igeta, M. and Hijikata, K., Experimental Study on Point Contact Transport Phenomena Using the Atomic Force Microscope, *Microscopical Thermophysical Engineering* **1997**, 1, 201.
42. Reifsnider, K.L., Modelling of the interphase in polymer-matrix composite material systems, *Composites* **1994**, 25, 461.

## ΠΕΡΙΛΗΨΗ

Συμβολή στην ανάδειξη της κατά Θεοχάρην μεσοφάσεως μέσω της μικροσκοπίας θερμικών δυνάμεων άτομικής κλίμακας

Παλαιότερες μελέτες για τον χαρακτηρισμό των περιοχών μεσοφάσεως σε θερμοσκληρυνόμενα σύνθετα υλικά έχουν οδηγήσει στο συμπέρασμα ύπαρξεως των περιοχών αυτών μέσω μηχανικών και θερμικών μετρήσεων μακροσκοπικής κλίμακας. Μετά την ανάπτυξη της μικροσκοπίας θερμικών δυνάμεων άτομικού επιπέδου και των αντιστοιχών αισθητήρων, έγινε δυνατή η μελέτη των θερμικών ιδιοτήτων των υλικών σε πολύ μικρότερη κλίμακα. Τοπικές μεταβολές των ιδιοτήτων αυτών σε αεροναυπηγικών προδιαγραφών θερμοσκληρυνόμενο σύνθετο υλικό με μήτρα ρητίνης και ενίσχυση από ίνες γυαλιού ή άνθρακα μετρήθηκαν με μικροσκόπιο αναλύσεως θερμικών δυνάμεων σε άτομική κλίμακα. Οι μετρηθείσες μεταβολές αναδεικνύουν σαφώς την παρουσία ενός μαλακού στρώματος μεσοφάσεως στο γυαλί και υπογραμμίζουν την σημασία των αλληλεπιδράσεων ίνας/μήτρας κατά την διαδικασία δημιουργίας της μεσοφάσεως. Διαπιστώθηκε ότι ο τύπος της ίνας έχει σημαντικό ρόλο στην

δημιουργία τῆς μεσοφάσεως. Πράγματι, οἱ μικροθερμικὲς μετρήσεις τῆς θερμοκρασίας μεταβάσεως ἐπιβεβαίωσαν τὴν παρουσία μεσοφάσεως στὴν περιοχὴ τῶν ἰνῶν ποὺ εἶναι κατασκευασμένες ἀπὸ γυαλί ἀλλὰ ὅχι ὅταν αὐτὲς προέρχονται ἀπὸ ἄνθρακα. Συμπερασματικῶς, ἡ παροῦσα ἐργασία προσφέρει μίαν νέα μεθοδολογία γιὰ τὴν ἄμεση μέτρηση τῶν θερμικῶν ἰδιοτήτων συνθέτων συστημάτων καὶ ἀναδεικνύει σαφῶς τὸν βαθμὸ ἐπιδράσεως αὐτῶν τῶν συστημάτων στὴν συμπεριφορὰ συνθέτων ὑλικῶν.